

Statistical theory of monodisperse linear polymers of finite semiflexibility: Bethe-Peierls approximation

F. F. Semeriyarov

Institut für Physik, Martin-Luther-Universität Halle, D-06099 Halle, Germany

(Dated: February 2, 2008)

We employ the Bethe-Peierls technique to obtain the self-consistent thermodynamic description for the system of linear semiflexible polymers of equal length. To our best knowledge, this is done rigorously for the first time. We show that the theory is in quantitative agreement with the Sanchez-Lacombe theory. The overall configurational entropy expression contains the athermal and the semiflexibility contributions and the correction due to the attractive interactions between monomers. Based on the paper by Wolfgardt et al. [Phys. Rev. E 54, 1535 (1996)], we conclude that the present theory captures the first two contributions better than the Gibbs-DiMarzio theory. The entropies of the states corresponding to high densities, obtained at low temperatures, high pressures and high molecular weights, extrapolate to negative values. This feature, known also as the Kauzmann paradox, is the thermodynamic manifestation of the glass transition. An investigation of the configurational specific heat dependence on molecular weight is also provided.

I. INTRODUCTION

In 1948, Kauzmann¹ recognized a peculiar feature of the thermodynamic behavior of liquids in the vicinity of glass transition. He found that the configurational entropy drops very rapidly with temperature decrease and does not seem to vanish close to absolute zero. It looks like the configurational entropy would instead drop to zero at a *positive* temperature, T_K , and, hence, something should happen to the system in order to avoid the entropy becoming negative at temperatures below T_K . The problem has attracted much theoretical attention after the work by Gibbs and Di Marzio². They demonstrated by means of a statistical calculation that the configurational entropy of a disordered polymer liquid extrapolates to the negative values at low temperatures. This violates the Nernst postulate and makes the problem very puzzling. To resolve this problem, they proposed that a second-order transition to a unique state, the ideal glass, would occur at $T = T_K$. Gujrati and Goldstein³ criticized the Gibbs-DiMarzio theory for the absence of a crystalline state. But, recently, Corsi and Gujrati⁴ presented a calculation where, besides the disordered liquid phase, the crystalline phase was captured and where the configurational entropy of the liquid phase would become negative at low temperatures as well. It was pointed out that, provided the stable crystalline state exists below the melting temperature, $T_M > T_K$, the unusual ideal-glass transition in the *metastable liquid region* by no means should violate the thermodynamic laws, see also⁵.

The issue of the crystalline state existence for complex polymer topologies is a very challenging theoretical problem. In the course of polymerization chains of progressively larger sizes are formed, which causes the increase in viscosity and eventually leads to the vitrification of the system. In the case when the polymerization coordination is larger than two, the polymers can be formed with branches extending in an irregular manner. This makes it difficult if not impossible to construct an ordered state in the system.

In the present paper we study a model of compressible polymer melt by means of a new treatment based on the Bethe-Peierls approximation. As in the Gibbs-DiMarzio theory, our calculation does not capture the ground state. The latter fact is, of course, a disadvantage of the method, but the level of prediction is qualitatively the same as in the more accurate theory⁴. We show that the present simple theory enjoys a quantitative agreement with experiment and can be used in connection with the work by Wolfgardt *et al.*⁶.

We consider the semiflexible linear x-mers distributed on a lattice. The penalty for a chain bend is introduced by means of the Flory's flexibility⁷, f . We also take into account the interactions among monomers assigning the energy, $V < 0$ (attractive interaction), to the nearest-neighbor pairs of occupied sites. The Bethe-Peierls approximation⁸ was originally developed for single site species. An extension of the method to diatomic species was provided by Chang⁹. The aim of the present paper is to extend the Chang's scheme further to polyatomic species. A geometrical interpretation of polymer semiflexibility, consistent with the Flory's definition of f , can also be provided, which is demonstrated in the following. The entropy expression is found to reduce to the Flory-Huggins form¹⁰ in the appropriate limit: $V = 0$ and $z \rightarrow \infty$, where z is the lattice coordination number.

A significant improvement to the Flory-Huggins theory is the lattice cluster theory (LCT) developed by Freed and co-workers (see¹¹ and references there in). The LCT not only provided a rigorous and systematic cluster expansion method for generating corrections to the Flory-Huggins theory, but also predicted the influence of monomer structure on thermodynamic properties analytically. However, the formalism is rather complicated, which impedes its wide use. In analogy to the Gibbs-DiMarzio theory, the LCT configurational entropy also extrapolates to zero at a positive temperature¹².

II. BETHE-PEIERLS APPROXIMATION

The main idea of the method is to calculate the grand partition function (GPF) for configurations of an aggregate composed of a molecule occupying a lattice site (internal site) and its z neighbors (surface sites) in the framework of a mean-field theory: An effective field is superimposed on the surface molecules by molecules outside the aggregate. It is determined making use of the condition of equal probability for the internal molecule as well as for any molecule from the aggregate surface to be in a particular configuration. After determination of the GPF other quantities such as energy (enthalpy at constant pressure), specific heat, etc. follow at once.

The effective interaction parameter, V , is defined as the energy of interaction between two occupied sites that are nearest-neighbors to each other irrespective of whether they are connected by a bond or not. To account for the presence of free volume, the lattice-hole model is employed in which monomers and holes (empty lattice sites) populate a lattice with the occupancy controlled by the system chemical potential, μ . The polymer semiflexibility is incorporated through U_f being the energetic penalty for creation of a chain bend. Based on this information, a general form of the GPF can be given:

$$Z = \sum \Omega(n, X, N_g, N) \eta^X \lambda^n w_f^{N_g}, \quad (1)$$

where $\eta = \exp(-V/k_B T)$ is the Boltzmann weight for the interactions between occupied sites, $\lambda = \exp(\mu/k_B T)$ is the absolute activity, $w_f = \exp(-U_f/k_B T)$ is the Boltzmann weight for the flex energy, n is the total number of occupied sites, X is the number of nearest-neighbor pairs of occupied sites, N_g is the total number of the gauche configurations, Ω is the number of arrangements on a lattice of N sites that have the same n , X , and N_g numbers.

For comparison purposes, it is instructive to begin by presenting the original Bethe-Peierls technique. Next, we are going to present a modification due to the chain connectivity. At first, the aggregate is pictured as a site surrounded by z surface sites. A set of numbers is defined: $\{\theta_i\} = \theta_0, \theta_1, \dots, \theta_z$, which are 0 or 1 according as the corresponding sites are empty or occupied, where the index $i = 0$ is reserved for the internal site. A configuration with the internal site being unoccupied ($0; \theta_1, \dots, \theta_z$) contributes to the GPF as the sum over all arrangements on the surface sites $\sum_{\{\theta_i\}} \lambda^{\theta_1 + \dots + \theta_z} \psi(\theta_1, \dots, \theta_z)$, where ψ is the field that couples the aggregate configurations to the uniform external distribution. Presuming there are no sites occupied by the segments of the same chain among the surface sites, two types of correlations generated by a local configuration can be identified: the occupancy of a surface site 1) means the possibility of the bond presence between the given site and an external nearest-neighbor site, 2) induces the mer-mer interaction with occupied external sites. An empty surface site does not induce any correlations to the exterior. These facts can be generally

taken into account assuming that ψ is given by

$$\psi = c \xi^{\theta_1 + \dots + \theta_z},$$

where c is some constant. From this follows that for the configuration ($0; \theta_1, \dots, \theta_z$) the GPF is given by

$$\sum_{\{\theta_i\}} c (\lambda \xi)^{\theta_1 + \dots + \theta_z} = c (1 + \lambda \xi)^z. \quad (2)$$

To study the linear chains, we consider the aggregate composed of x sites and their $z' = 2(z-1) + (x-2)(z-2)$ next neighbors. The modification was inspired by the papers published quite some time ago^{9,13}, which makes us a little unsure about the novelty of the result, but we are unaware of any related work.

The GPF for the configuration ($1, \dots, 1; \theta_{x+1}, \dots, \theta_{x+z'}$) can be represented in the following general form:

$$\sum_{i_2 i_3 \dots i_x} \sum_{\{\sum^j\}} c_x \lambda^x \eta^{x-1} (\lambda \eta \xi_x)^{\sum^2 \theta + \dots + \sum^x \theta}, \quad (3)$$

where the first sum is over configurations permitted by the linear chain topology, the second sum is over configurations on the surface sites, the factor η^{x-1} takes into account the interactions among the segments of the chain inside the aggregate, and $\sum^j \theta = \theta_1 + \dots + \theta_{j-1} + \theta_{j+1} + \theta_x$. In order to calculate (3), we propose a recursive method analogous to the Bethe lattice technique¹⁴. Accordingly, the aggregate composed of a site and its z neighboring sites corresponds to the center of the Bethe lattice, an infinite Cayley tree, which is a connected dendritic structure with constant coordination, z , and no loops. As before, the configurations with the central site being unoccupied are included in the GPF by the term $c(1 + \lambda \xi)^z$, where ξ represents the effective field for the case when no bond is present inside the aggregate. For the case when the central site is occupied by an end-point or by a middle group, we define χ_k to account for correlations induced by the chain connectivity; where k is the number of bonds in the chain piece extending beyond the surface site of the aggregate. The GPF can be formulated as follows:

$$Z = c(1 + \lambda \xi)^z + cz(1 + \lambda \eta \xi)^{z-1} \lambda^2 \eta \chi_{x-1} + c \frac{z}{2} r_f (1 + \lambda \eta \xi)^{z-2} \lambda^3 \eta^2 \sum_{k=1}^{x-2} \chi_k \chi_{x-k-2}, \quad (4)$$

where the factor z in the second term is the number of orientations for the bond extending from the end-point occupying the internal site of the aggregate; in the third term, the factor

$$r_f = w_f(z-2) + 1 \quad (5)$$

takes into account the semiflexibility. The latter is derived making use of the assumption that the number of trans configurations in the aggregate is equal to $z/2$. In the case when z is an even number and the surface sites, situated around the internal (central) site, are equally

spaced among each other, $z/2$ is easily identified as the number configurations of two bonds with the 180 degree angle between them. Note that this naive picture cannot be used for the case when z is an odd number and the surface sites are equally spaced around the internal site, since a construction of trans configurations with the 180 degree angle between the bonds is not possible in 2-D space (we are not sure about the 3-D case). Proceeding further with our description of (4), we justify the statistical weight $zr_f/2$ by means of the relation

$$\left[\frac{z(z-1)}{2} - \frac{z}{2} \right] w_f + \frac{z}{2} = \frac{z}{2} r_f,$$

where $z(z-1)/2$ is the total number of possible configurations for two bonds inside the aggregate. In order to evaluate the GPF, we obtain the Behte lattice recursive relations for χ_k :

$$\begin{aligned} \chi_1 &= c'(1 + \lambda\eta\xi)^{z-1}, \\ \chi_2 &= c'r_f\lambda\eta(1 + \lambda\eta\xi)^{z-2}\chi_1, \\ &\vdots \\ \chi_k &= c'r_f\lambda\eta(1 + \lambda\eta\xi)^{z-2}\chi_{k-1}, \end{aligned}$$

where the factor r_f and the power $z-2$ are due to the fact that there are $z-2$ local gauche conformations out of $z-1$ possible for a middle segment located anywhere except the center of the Bethe lattice, c' is a scaling factor measuring the distance from the Bethe lattice center to be evaluated in the following. The summation in the third term of (4) can now be carried out to yield

$$\sum_{k=2}^{x-1} \chi_k \chi_{x-k-2} = (x-2)(c'r_f\lambda\eta)^{x-3}(1 + \lambda\eta\xi)^{(x-3)(z-2)}\chi_1^2$$

Finally, we find

$$Z = c(1 + \lambda\xi)^z + cc'^{x-1}\frac{z}{2}r_f^{x-2}x\lambda^x\eta^{x-1}(1 + \lambda\eta\xi)^{z'}. \quad (6)$$

Therefore, the function ψ for this configuration appears to be

$$c_x\gamma x\lambda^x\eta^{x-1}(\lambda\eta\xi_x)^{\theta_{x+1}+\dots+\theta_{x+z'}},$$

where γ is the number of ways per site the polymer chain can be arranged on otherwise empty lattice. We find that $\gamma_{\text{flex}} = \frac{z}{2}(z-1)^{x-1}$ for completely flexible chains, $\gamma_{\text{rigid}} = \frac{z}{2}$ for rigid rods, and $\gamma_{\text{flex}} = \frac{z}{2}[w_f(z-2)+1]^{x-1}$ for semiflexible chains. The GPF for this configuration will be

$$c_x\gamma x\lambda^x\eta^{x-1}(1 + \lambda\eta\xi_x)^{z'},$$

where the constants c_x and ξ_x can be related to c and ξ , respectively: We write the GPF for the aggregate with the empty internal site and one empty surface site, and compare it with the GPF written for the aggregate with two empty sites being internal. The former is obtained summing over all θ 's on $z-1$ surface sites, which results $\sum_{\{\theta_i\}} c(\lambda\xi)^{\theta_2+\dots+\theta_z}$. The latter is evaluated by summing over $2(z-1)$ surface sites: $\sum_{\{\theta_i, \theta'_i\}} c_2(\lambda\xi_2)^{\theta_2+\dots+\theta_z+\theta'_2+\dots+\theta'_z}$. Both partition functions should be the same, hence the relations $\xi = \xi_2$ and $c = c_2(1 + \lambda\xi)^{z-1}$ are valid, as found by performing the summation over various configurations $\theta'_2, \dots, \theta'_z$. This idea can be applied for aggregates of larger sizes. Our suggestion: since the chains consist of $x-1$ bonds each, the relation should be

$$\xi = \xi_x \quad \text{and} \quad c = c_x(1 + \lambda\xi)^{(z-1)(x-1)}, \quad (7)$$

which yields

$$Z = c(1 + \lambda\xi)^z + c_x\gamma x\lambda^x\eta^{x-1}(1 + \lambda\eta\xi)^{z'}, \quad (8)$$

which is identical to (6) provided $c' = (1 + \lambda\xi)^{-(z-1)}$.

Having established the GPF, we now turn to the detailed study of the equal probability condition for absorption at the internal site and surface sites. Note also that this probability is the fractional coverage of the lattice $\theta = n/N$. The following pair of equations

$$\begin{aligned} \theta &= Z^{-1} \sum_{i_2 i_3 \dots i_x \{\sum^j\}} \sum c_x \lambda^x \eta^{x-1} (\lambda\eta\xi_x)^{\sum^2 \theta + \dots + \sum^x \theta} \\ &= Z^{-1} c_x \gamma x \lambda^x \eta^{x-1} (1 + \lambda\eta\xi)^{z'} \end{aligned} \quad (9)$$

and

$$\begin{aligned} \theta &= (zZ)^{-1} c \sum_{\{\theta_i\}} (\theta_1 + \dots + \theta_z) (\lambda\xi)^{\theta_1 + \dots + \theta_z} \\ &\quad + (zZx)^{-1} c_x \sum_{i_2 i_3 \dots i_x \{\sum^j\}} \underbrace{(1 + \dots + 1)}_{x-1} + \sum^2 \theta + \dots + \sum^x \theta \lambda^x \eta^{x-1} (\lambda\eta\xi)^{\sum^2 \theta + \dots + \sum^x \theta} \\ &= (zZ)^{-1} c \xi \frac{\partial}{\partial \xi} (1 + \lambda\xi)^z + (zZx)^{-1} c_x \gamma \lambda^x \eta^{x-1} \left(2(x-1)(1 + \lambda\eta\xi)^{z'} + \xi \frac{\partial}{\partial \xi} (1 + \lambda\eta\xi)^{z'} \right), \end{aligned} \quad (10)$$

are obtained in analogy with the corresponding equations

from Ref. 9. Combining Eqs. (9) and (10), one finds the

equations of state:

$$\frac{\theta}{1-\theta} = \frac{zx}{z'} \frac{\varepsilon(1+\eta\varepsilon)}{1+\varepsilon} \quad (11)$$

$$\gamma x \eta^{x-1} \lambda^x = \frac{x\varepsilon}{z'} \frac{(1+\varepsilon)^{x-2+z'}}{(1+\eta\varepsilon)^{z'-1}}, \quad (12)$$

where $\varepsilon = \lambda\xi$. The solution of the quadratic equation (11) is given by

$$\varepsilon(\theta) = \varepsilon_+ = \frac{\theta z' - (1-\theta)zx + D}{2zx\eta(1-\theta)}, \quad (13)$$

where

$$D = \sqrt{[\theta z' - (1-\theta)zx]^2 + 4z'zx\eta\theta(1-\theta)}.$$

Another solution with the negative sign before D in (13) is physically irrelevant, since $\varepsilon_- = -1$ in the athermal limit $\eta = 1$, while $\varepsilon_+ = z'\theta/zx(1-\theta) > 0$ in this case.

There is another method to derive (11) and (12): The occupation θ is obtained as the ratio of the term corresponding to the occupied internal site to the total partition function:

$$\theta = Z^{-1} c \frac{z}{2} r_f^{x-2} x \lambda^x \eta^{x-1} (1+\lambda\xi)^{-(x-1)(z-1)} (1+\lambda\eta\xi)^{z'} \quad (14)$$

This allows us to derive (12):

$$\frac{z}{2} r_f^{x-2} x \lambda^x \eta^{x-1} = \frac{\theta}{1-\theta} \frac{(1+\lambda\xi)^{x-1+z'}}{(1+\lambda\eta\xi)^{z'}}, \quad (15)$$

It should also be considered that the probability to find the internal site of the aggregate unoccupied can be calculated by two methods:

$$Z^{-1} c (1+\lambda\xi)^z$$

and

$$Z^{-1} c \{ (1+\lambda\xi)^{z-1} + (z-1)\lambda^2\eta(1+\lambda\eta\xi)^{z-2} \chi_{x-1} + \frac{z-2}{2} r_f (1+\lambda\eta\xi)^{z-3} \lambda^3 \eta^2 \sum_{k=2}^{x-1} \chi_k \chi_{x-k-1} \},$$

where the quantity in the curly brackets is the partial partition function for the surface z sites calculated under the condition that the internal site is empty. Thus, with aid of (15), we obtain

$$(1+\lambda\xi)^z = (1+\lambda\xi)^{z-1} + \frac{z'}{zx} \frac{\theta}{1-\theta} \frac{(1+\lambda\xi)^z}{(1+\lambda\eta\xi)},$$

which can be reduced to (11).

To this end we remark that one can also derive these equations solely from the kinetic considerations for molecular absorption/desorption process¹⁵. Here we provide only the derivation of the first equation to save space. In the aggregate represented by a site surrounded by z sites, the probability for a configuration $(0; \theta_1, \dots, \theta_z)$

to occur is assumed to be proportional to $\phi^{\theta_1+\dots+\theta_z}$, where ϕ is the quantity to be determined further. Then, the probability for the internal site to be unoccupied should be proportional to $\sum_{\{\theta_i\}} \phi^{\theta_1+\dots+\theta_z} = (1+\phi)^z$. Hence, the probability for one of its z neighbors to be occupied is given by

$$\frac{\sum \theta_i \phi^{\theta_1+\dots+\theta_z}}{(1+\phi)^z} = \frac{\phi(1+\phi)^{z-1}}{(1+\phi)^z} = \frac{\phi}{1+\phi}. \quad (16)$$

For the aggregate enclosing a chain with its neighborhood, the probability for any of the surface sites to be occupied, provided all internal sites are empty, is calculated in the analogous manner and is given by

$$\frac{\bar{\phi}}{1+\bar{\phi}}, \quad (17)$$

where $\bar{\phi}$ is the quantity similar in nature to ϕ . Comparing (16) and (17), one gets $\bar{\phi} = \phi$. The probabilities for various states of occupation of the surface sites, provided that all x internal sites are occupied, are proportional to $(\eta\xi)^{\theta_{x+1}+\dots+\theta_{x+z'}}$, which gives

$$\frac{\eta\bar{\phi}}{1+\eta\bar{\phi}}$$

for the probability of a surface site to be occupied when the internal sites are also occupied. The condition is

$$\theta = (1-\theta) \frac{\phi}{1+\phi} + \theta \left(\frac{2(x-1)}{zx} + \frac{z'}{zx} \frac{\eta\phi}{1+\eta\phi} \right),$$

where $[2(x-1)/zx]\theta$ is the ratio of number of bonds $2(x-1)\theta/zx$ per lattice site to the total number of lattice bonds $z/2$ per lattice site representing the probability to have a bond extending from an occupied site. The equation (11) follows immediately taking

$$\phi = \varepsilon.$$

III. THERMODYNAMICS

Further analysis of (1) can be carried out to derive the configurational entropy expression. First, we write the partition function as

$$Z = \sum \Omega \lambda^n \eta^X w_f^{N_g} = \sum e^{N(\theta g(\theta) + \theta \ln \lambda + \theta_X \ln \eta + \theta_g \ln w_f)},$$

where $\theta_X = X/N$, and $\theta_g = N_g/N$. The minimal free energy can be achieved applying the condition:

$$\frac{\partial}{\partial \theta} [\theta g(\theta) + \theta \ln \lambda + \theta_X \ln \eta + \theta_g \ln w_f] = 0.$$

Thus, the configurational entropy is given by

$$S_N/k_B = [\theta g(\theta)]^* \\ = - \int \ln \lambda d\theta - \theta_X \ln \eta - \theta_g \ln w_f, \quad (18)$$

where S_N is the entropy per lattice site. Note, $g^*(0) = 0$, $\theta_X(0) = 0$, and $\theta_g(0) = 0$. It is appropriate to define the entropy per monomer:

$$S_n = S_N/\theta.$$

After integration of (18), the entropy expression adopts the form

$$S_n/k_B = \frac{1}{x} \ln(\gamma x \eta^{x-1}) - \frac{1}{x} \ln \theta - \frac{(1-\theta)}{\theta} \ln(1-\theta) \\ + \frac{(x-1)(1-\theta)}{x\theta} \ln[(1+\varepsilon)(1-\theta)] \\ + \frac{z'}{x} \ln \theta + \frac{z'}{x} \frac{(1-\theta)}{\theta} \ln(1-\theta) \quad (19) \\ - \frac{z'}{x} \ln\left(\frac{zx\varepsilon}{z'}\right) + \frac{z'}{x} \frac{1}{2\theta} \ln\left(\frac{1+\varepsilon}{1-\theta}\right) \\ + E_n/k_B T,$$

where $E_n/k_B T = -(\theta_X \ln \eta + \theta_g \ln w_f)/\theta$ is the system internal energy per monomer.

The contact density θ_X is evaluated making use of the lattice topological relations:

$$z\theta = 2\theta_X + \theta_{X'}, \\ z(1-\theta) = 2\theta_{X''} + \theta_{X'},$$

where $\theta_{X'}$ is the density of pairs formed by an empty site adjacent to an occupied and $\theta_{X''}$ is the density of nearest-neighbor pairs formed by empty sites. We calculate $\theta_{X''}$ from the fact that the probability of having an empty site being a neighbor to another empty site is, in accordance with (16), equal to $1/(1+\varepsilon)$, and taking into account that there are on average $z/2$ lattice bonds per site:

$$\theta_{X''} = \frac{z}{2} \frac{(1-\theta)}{1+\varepsilon}.$$

Then, we have

$$\theta_X = z\theta - \frac{z}{2} + \frac{z}{2} \frac{(1-\theta)}{1+\varepsilon}. \quad (20)$$

The density of the gauche bonds θ_g is given by

$$\theta_g = \frac{\theta}{x}(x-2) \frac{(z-2)w_f}{1+(z-2)w_f}, \quad (21)$$

where θ/x is the number of polymers, $(x-2)$ is the number of middle groups in each polymer, and the factor

$$f = (z-2)w_f/[1+(z-2)w_f] \quad (22)$$

is the probability to form the gauche configuration derived by Flory⁷. The latter can be obtained from our

theory as well: The density of gauche bonds θ_g is the ratio of

$$\frac{z(z-1)}{2} - \frac{z}{2} = \frac{z(z-2)}{2}$$

terms corresponding to the gauche configurations in (4) to the total the GPF:

$$\theta_g = \frac{(z/2)(z-2)w_f(x-2)\lambda^x \eta^{x-1}(1+\lambda\xi)^{-(x-1)(z-1)}(1+\lambda\eta\xi)^{z'}}{Z},$$

which, by use of Eq. (14), can be written in the more compact form:

$$\theta_g = \theta \frac{x-2}{x} \frac{w_f}{r_f}.$$

This completes our proof of (21).

The equilibrium properties of the system can be deduced from the thermodynamic identity

$$\mu = H_n - TS_n, \quad (23)$$

where the configurational enthalpy per monomer, $H_n = E_n + Pv_0/\theta$, with v_0 being the volume of a lattice site. By aid of Eq. (12) the density dependence of the chemical potential, $\mu = k_B T \ln \lambda$, arises straightforwardly:

$$\mu = -\frac{k_B T}{x} \ln(\gamma x \eta^{x-1}) + \frac{k_B T}{x} \ln\left(\frac{\theta}{1-\theta}\right) \\ + \frac{k_B T}{x} (x-1) \ln(1+\varepsilon) + z' \ln\left(\frac{1+\varepsilon}{1+\eta\varepsilon}\right).$$

Performing further algebraic manipulations, we derive

$$Pv_0/k_B T = \frac{z}{2} \ln(1+\varepsilon) + \frac{z-2}{2} \ln(1-\theta). \quad (24)$$

The equation (24) serves as the implicit equation for determination of θ .

Making use of the relations for the densities, Eq. (19) can be written in a slightly different form

$$S_n/k_B = \frac{1}{x} \ln \frac{z}{2} + \frac{\ln x}{x} - \frac{\ln \theta}{x} - \frac{(1-\theta)}{\theta} \ln(1-\theta) \\ + \frac{(x-1)(1-\theta)}{x\theta} \ln[(1+\varepsilon)(1-\theta)] \\ + \frac{z'}{x} \ln \theta + \frac{z'}{x} \frac{(1-\theta)}{\theta} \ln(1-\theta) \quad (25) \\ - \frac{z'}{x} \ln\left(\frac{zx\varepsilon}{z'}\right) + \frac{z'}{x} \frac{1}{2\theta} \ln\left(\frac{1+\varepsilon}{1-\theta}\right) \\ - \frac{(\theta_X - \theta_b) \ln \eta}{\theta} \\ - \frac{x-2}{x} [f \ln f + (1-f) \ln(1-f) \\ - f \ln(z-2)],$$

where θ_b is the bond density given by $\theta_b = (x-1)\theta/x$.

The equations (24) and (13) are to be solved numerically for θ as a function of T at constant P . We then

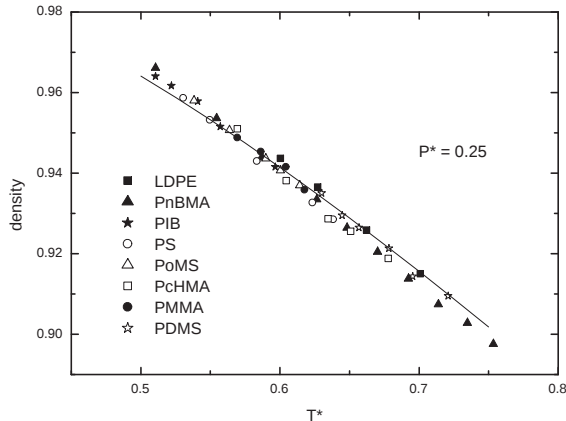


FIG. 1: Test of Eq. (24) against experimental data for various polymer liquids.

substitute θ and $\varepsilon(\theta)$ calculated from (13) into (25) to obtain the entropy at a constant pressure. Finally, configurational heat capacity per occupied site, C_p , can be computed from

$$C_p = (\partial H_n / \partial T)_p$$

or equally from

$$C_p = T(\partial S_n / \partial T)_p.$$

According to our numerical computation, both identities produce the same specific heat, which indicates that the present theory is thermodynamically self-consistent.

IV. COMPARISON WITH OTHER RESULTS

In the present section, we analyze the main characteristics of the thermodynamic functions (24) and (25) in comparison with data available from experiments and simulations.

Presented as early as in 1976, the lattice fluid (LF) theory developed by Sanchez and Lacombe¹⁶, due to its simplicity and high level of prediction, became a foundation of many successional theoretical and experimental investigations of polymer systems¹⁷. In analogy with the LF theory, the equation of state (24) can be written in terms of the reduced temperature $T^* = -2k_B T / zV$ and pressure $P^* = -2v_0 T / zV$. Figure 1 shows the experimental data for density, θ , vs. reduced temperature, T^* , obtained from Fig. 3 of Ref. 18 for various liquids. The line is the theoretical isobar ($T^* = 0.25$) computed applying the limit $x \rightarrow \infty$ for $z = 20$. Based on this we conclude that the present theory adequately describes the relationship of density, temperature, and pressure for pure polymer fluid.

The important difference between the theory by Sanchez and Lacombe and the present theory is in entropy. The LF entropy is independent of temperature, while (25) exhibits a temperature dependence. This is a consequence of consideration of the configurational distribution of the polymer system influenced by mer-mer interaction energy and polymer semiflexibility, which is absent in the LF theory.

At this point we would like to note that the results from the Monte Carlo (MC) simulations by Wolfgart *et al.*⁶ could be used *in support* of the present theory. These MC simulations revealed that, for the case of semiflexible non-interacting polymer, the Milchev's entropy expression¹⁹

$$S_M / k_B = \frac{1}{x} \ln \frac{z}{2} + \frac{\ln x}{x} - \frac{\ln \theta}{x} - \frac{(1-\theta)}{\theta} \ln(1-\theta) \quad (26) \\ - \frac{x-2}{x} [f \ln f + (1-f) \ln(1-f) - f \ln(z-2)].$$

is more accurate than that by Gibbs and DiMarzio. The Milchev's expression is recovered from (25) setting $V = 0$, which could be easily verified. Thus, our theory is capable of capturing the athermal part and the semiflexibility part of the configurational entropy at constant pressure more accurately than the previous lattice theories^{2,19}. However, we disagree with the conclusions of Ref.⁶ regarding the relevance of the Gibbs-DiMarzio work. Our point of view will be disclosed in the next Section.

V. KAUZMANN PARADOX

Typical curves of entropy vs. reduced temperature for various values of the flex energy, incorporated in the parameter $T_f^* = z U_f / 2$, are shown in Fig. 2. As evident from the graph, the configurational entropy vanishes at a positive temperature T_K^* , and the lower the flex energy the smaller this temperature is. It is important to notice that, for small flex energies, the entropy behaves like it has reached a stable level just before the rapid drop for T^* near T_f^* . Thus, in an experiment, being unable to cool the system down to temperatures below T_f^* one might wrongly conclude that the entropy extrapolates to a positive value at $T = 0$.

We understand that no state in Nature could by any chance have a negative entropy. Therefore, the prediction of solutions corresponding to negative entropies must be an artificial feature of a model and these solutions should be replaced by a unique state where the system gets trapped under further cooling, i.e. the ideal glass state, see⁵.

The principal contribution that makes the entropy negative is $-\frac{(\theta_x - \theta_b) \ln \eta}{\theta}$, which is one of the terms of the thermal correction due to the attractive mer-mer interaction. It remains relatively constant over a wide temperature range, while other positive contributions reduce with temperature decrease. The flexibility term vanishes because the polymers becoming stiffer lose their internal

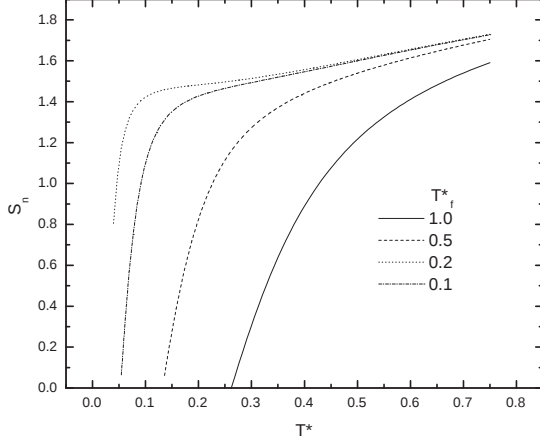


FIG. 2: Configurational entropy dependence on reduced temperature for different values of T_f^* calculated taking $P^* = 0.25$, $z = 12$, $x = 1000$.

degrees of freedom. In the limit of infinitely low temperatures $f \rightarrow 0$ and, hence, $[f \ln(f) + (1 - f) \ln(1 - f) - f \ln(z - 2)] \rightarrow 0$. This suggests that the results of the Monte Carlo simulations by Wolfgardt *et. al.*⁶ cannot be used to doubt the relevance of the Kauzmann paradox due to the absence of the interaction between monomers.

Another interesting aspect of the glass transition is the existence of routes of vitrification alternative to supercooling such as polymerization and compression by pressure. The first investigation of molecular weight dependence of the ideal glass transition is contained in the original paper by Gibbs and Di Marzio². Figure 3 presents configurational entropy vs. chain length at a constant pressure plotted for various temperatures. The curves have a common behavior: the entropy is a monotonically decreasing function of molecular weight, and the lower the temperature the smaller the entropies are. When a curve crosses $S_n = 0$ ordinate at x_K , further molecular weight growth is thermodynamically prohibited, which signals the glass transition to occur during polymerization at some $x_g < x_K$. Entropy curves descend rapidly at initial stages of equilibrium polymerization, then the curves become almost flat although not bounded by a horizontal asymptote. Even a minute temperature difference can influence x_K dramatically. This situation is clearly reflected in Fig. 3, where the solid and the dashed lines correspond to $T^* = 0.26287$ and $T^* = 0.264$, respectively, and $T_f^* = 1.0$ and $P^* = 0.25$ were used. Based on this one can introduce an effective temperature above which entropy is practically always positive. Calculated as accurately as in 5 decimal digits, due to high sensitivity of entropy, this temperature is $T^* = 0.26287$ for $T_f^* = 1.0$ and $P^* = 0.25$.

The states with negative entropies are also produced

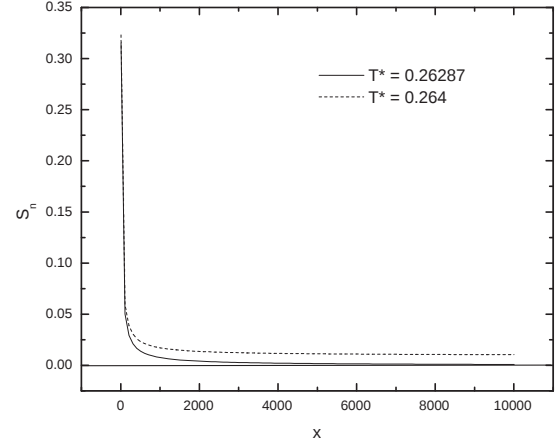


FIG. 3: Configurational entropy vs. chain length, $P^* = 0.25$, $z = 12$, $T_f^* = 1.0$. This demonstrates the ideal-glass transition at high molecular weights and low temperatures that corresponds to the system vitrification during polymerization reactions conducted at sufficiently low temperatures.

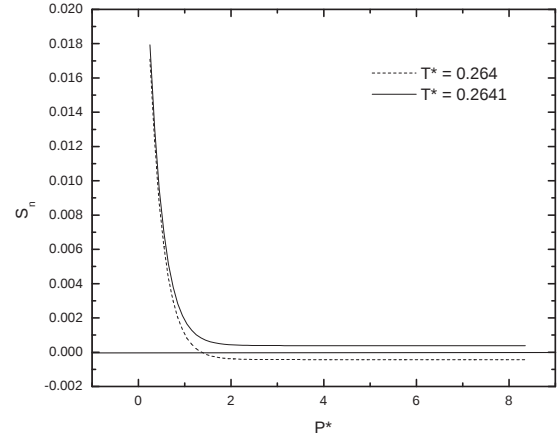


FIG. 4: Configurational entropy vs. pressure, $x = 1000$, $z = 12$, $T_f^* = 1.0$. This is the demonstration of the ideal-glass transition generated by a combination of low temperatures and high pressures.

at elevated pressures below a certain temperature. The shape and the sensitivity of the curves in Fig. 4 are similar to the previous case. The entropy is practically flat at high pressures and is very sensitive to T^* . Taking $T_f^* = 1.0$ we find that the entropies cross the $S_n = 0$ ordinate for the temperatures below $T^* = 0.264$. In this case the point where the entropy turns negative, $P^* = P_K^*$, is the thermodynamic manifestation of the glass transition for $P_g^* < P_K^*$. The present theory is in qualitative

VII. CONCLUSION

We provide a very careful derivation of the entropy and the pressure expressions based on the Bethe-Peierls approximation for the model of polymer melt. The prediction of the system density at a given reduced pressure and temperature is shown to be in quantitative agreement with the experimental data obtained from¹⁸. The overall configurational entropy of the polymer fluid consists of three fundamentally different types of contributions, i.e., the athermal entropy (translational and configurational degrees of freedom), the semiflexibility correction entropy, and the thermal correction entropy that is due to the thermal correction term of the partition function. The third type, that is absent in the Flory-Huggins theory and in the LF theory by Sanchez and Lacombe, contributes the main part at low temperatures. We also demonstrate that our theory is equivalent to the Ryu-Gujrati theory with the correction due to chain semiflexibility.

The present work suggests that the thermodynamic scenario of the glass transition proposed by Kauzmann is relevant for the vitrification in the course of a polymerization as well as in the case of the compression under a sufficiently high pressure. We obtain the negative entropy states at certain conditions: low temperatures, $T \in [0..T_K]$, and some fixed pressure; high pressures, $P \in [P_K..\infty)$, and a fixed temperature; high molecular weights, $x \in [x_K..\infty)$, while both temperature and pressure are kept constant. These results are in quantitative agreement with earlier work by Di Marzio *et al.*^{2,20}.

Our computation of the configurational specific heat as a function of chain length revealed that this function is monotonically increasing at low temperatures and monotonically decreasing at high temperatures. In the transition region the function has a minimum.

VIII. ACKNOWLEDGMENTS

I would like to thank Dr. G.P. Johari for suggestion of the project. I am also very grateful to Dr. P.D. Gujrati for various helpful discussions. The support from the Deutsche Forschungsgemeinschaft (SFB 418) is gratefully acknowledged.

IX. APPENDIX

In this appendix we demonstrate that the entropy expression developed in the paper by Ryu and Gujrati¹⁴ with added correction due to polymer semiflexibility is equivalent to (25). Formulated for multicomponent mixtures their theory can easily be adopted to our system with minor corrections. One of these is due to discrepancy in methodology of accounting for the mer-mer interaction. In their theory this interaction is incorporated (as in the Flory-Huggins theory) through the *effective* interaction between occupied sites and vacancies with the

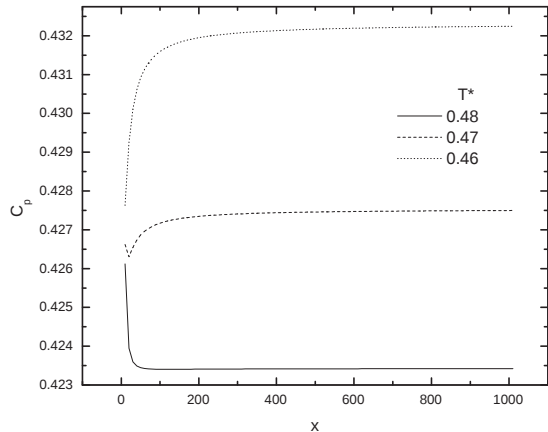


FIG. 5: Three typical dependencies of the configurational specific heat on chain length. For this figure we used $T_f^* = 0.5$, $P^* = 0.25$, $z = 12$.

agreement with the work by Di Marzio *et al.*²⁰.

VI. SPECIFIC HEAT

One of applications of this theory could be a comparison with experimental results available from literature for specific heat dependence on molecular weight. The specific heat of linear n -alkanes as a function of the number of carbons in the backbone is found to be a monotonically decreasing function²¹, while the specific heat of a continuously polymerizing system was measured to pass through a maximum²². We suggest that the controversy can be resolved in the framework of the present theory by studying the configurational specific heat as a function of chain length. Figure 5 shows C_p vs. x in three cases: $T^* = 0.48, 0.47, 0.46$ represented by continuous, dashed, and dotted lines, respectively; in all three cases $T_f^* = 0.5$. By showing this we want to demonstrate three types of typical behavior: for high temperatures ($T^* = 0.48$ and above) the curve is always sharply decreasing, then reaching a constant value; for low temperatures ($T^* = 0.46$ and below) the curve is monotonically increasing; in the intermediate region, the curve initially decreases reaches a minimum and then increases. This disagrees with the statistical calculation by Wang and Johari²³. As was shown by Di Marzio and Dowell²⁴ the specific heat has a large vibrational part. Hence, the specific heat maximum observed by Johari *et al.*²² during a polymerization reaction could be due to a freezing of the vibrational degrees of freedom as polymers become longer.

energy given by

$$\epsilon_{10} = e_{10} - 1/2(e_{11} + e_{00}),$$

where e_{10} , e_{11} , e_{00} are the energies of physical interactions for mer-hole, mer-mer and hole-hole pairs, respectively. Since only the second is actually present, $e_{01} = 0$, $e_{11} = V$, $e_{00} = 0$, one gets $\epsilon_{10} = -V/2$, with $w = \exp(V/2RT)$ being the corresponding Boltzmann weight. Note also that q in their symbolic representation is equivalent to z in ours - both signifying the coordination number. The semiflexibility can be incorporated replacing $r = q - 1$ in their paper by r_f defined in (5) and adding the term $-N_g \ln w_f$ to the entropy [see Eq. (28) below]. Here we summarize the results of their theory. The final equations resulting from the Bethe lattice iterative technique are

the following:

$$\begin{aligned} y_{0,1} &= (w + \lambda_1 y_1^{x-1} y_{0,1}^{z-1} / r_f) / (1 + w \lambda_1 y_1^{x-1} y_{0,1}^{z-1} / r_f), \\ 1/(1-\theta) &= 1 + (z/2) x y_{0,1}^z y_1^{x-1} / r_f, \\ Q_1 &= 1 + w \lambda_1 y_1^{x-1} y_{0,1}^{z-1} / r_f, \end{aligned}$$

where $\lambda_1 = (z/2)x - (x-1)$ and the parameters $y_1, y_{0,1}, Q_1$ are evaluated from the relations

$$y_{0,1} = \left[-w(p-1) + \sqrt{w^2(p-1)^2 + 4p} \right] / 2, Q_1 = 1 + wp/y_{0,1},$$

with $p = \theta \lambda_1 / (z/2)(1-\theta)x$. Below we list the expressions for the densities which are numbers of the corresponding species per lattice site:

$$\begin{aligned} \phi_{n,1} &= \theta/x, \quad \phi_b = \phi_{n,1}(x-1), \quad \phi_{00} = z(1-\theta)/Q_1, \quad \phi_{01} = z(1-\theta) - 2\phi_{00}, \\ \phi_{11} &= (z/2)\theta - \phi_{01} - \phi_b, \quad \phi_{1u} = (z/2)\theta - \phi_b, \quad \phi_{0u} = (z/2)(1-\theta), \\ \phi_u &= z/2 - \phi_b, \quad \phi_{11}^0 = \phi_{1u}^2/\phi_u, \quad \phi_{00}^0 = \phi_{0u}^2/\phi_u, \quad \phi_{01}^0 = 2\phi_{0u}\phi_{1u}/\phi_u, \end{aligned}$$

where $\phi_{n,1}$ and ϕ_b are the densities of polymers and bonds, respectively; ϕ_{00} , ϕ_{01} and ϕ_{11} are the densities of hole-hole, hole-mer and mer-mer nearest-neighbor contacts; ϕ_{00}^0 , ϕ_{01}^0 and ϕ_{11}^0 are the corresponding athermal contact densities; ϕ_{1u} and ϕ_{0u} are the densities of unoccupied lattice bonds associated with occupied sites and vacancies, respectively; ϕ_u is the density of unoccupied lattice bonds. The adimensional pressure, $\omega = \beta P v_0$ ($\beta = 1/k_B T$), given by

$$\beta P v_0 = -\ln(1-\theta) + (z/2) \ln(2\phi_u/z) + (z/2) \ln(\phi_{00}^0/\phi_{00}).$$

can be transformed to the form equivalent to (24):

$$\beta P v_0 = -\ln(1-\theta) + (z/2) \ln[(1-\theta)Q_1]. \quad (27)$$

Finally, we compared the Ryu-Gujrati configurational entropy corrected to account for semiflexibility,

$$\begin{aligned} S_n/k_B &= (\phi_{n,1} \ln[(z/2)r_f^{x-2}x/\phi_{n,1}] - (1-\theta) \ln(1-\theta) \\ &+ \phi_{01} \ln(\phi_{01}^0/\phi_{01}) + \phi_{00} \ln(\phi_{00}^0/\phi_{00}) + \phi_{11} \ln(\phi_{11}^0/\phi_{11}) - N_g \ln w_f)/\theta, \end{aligned} \quad (28)$$

with (27) and verified numerically that they are equivalent.

¹ W. Kauzmann, Chem. Rev. **43**, 219 (1948).

² J.H. Gibbs and E.A. DiMarzio, J. Chem. Phys. **28**, 373 (1958).

³ P.D. Gujrati, J. Phys. A: Math. Gen. **13**, L437 (1980); P.D. Gujrati and M. Goldstein, J. Chem. Phys. **74**, 2596 (1981).

⁴ P.D. Gujrati and A. Corsi, Phys. Rev. Lett. **87**, 025701 (2001); A. Corsi and P.D. Gujrati, Phys. Rev. E. **68**, 031502 (2003).

⁵ P.D. Gujrati, cond-mat/0309143.

⁶ M. Wolfgardt, J. Baschnagel, W. Paul, and K. Binder, Phys. Rev. E **54**, 1535 (1996).

- ⁷ P.J. Flory, Proc. R. Soc. London Ser. A **234**, 60 (1956); P.J. Flory, Proc. Natl. Acad. USA **79**, 4510 (1982).
- ⁸ H.A. Bethe, Proc. Roy. Soc. A **150**, 552 (1935); R. Peierls, Proc. Roy. Soc. A **154**, 207 (1936).
- ⁹ T.S. Chang, Proc. Camb. Phil. Soc. **35**, 265 (1939).
- ¹⁰ P.J. Flory, J. Chem. Phys. **10**, 51 (1942); M.I. Huggins, Ann. (N.Y.) Acad. Sci. **43**, 1 (1942).
- ¹¹ K.F. Freed and J. Dudowicz, Adv. Polym. Sci. **183**, 63 (2005).
- ¹² J. Dudowicz, K.F. Freed and J.F. Douglas, J. Chem. Phys. **124**, 064901 (2006).
- ¹³ A.R. Miller, Proc. Camb. Phil. Soc. **38**, 109 (1941); A.R. Miller, Proc. Camb. Phil. Soc. **39**, 54 (1943).
- ¹⁴ J.-H. Ryu and P.D. Gujrati, J. Chem. Phys. **107**, 3954 (1997).
- ¹⁵ J.K. Roberts, Proc. Roy. Soc. A **161**, 141 (1937).
- ¹⁶ I.C. Sanchez and R.H. Lacombe, J. Phys. Chem. **80**, 2352 (1976); R. H. Lacombe and I.C. Sanchez, J. Phys. Chem. **80**, 2568 (1976);
- ¹⁷ I.C. Sanchez in Polymer Blends Vol. 1, Ed. D. R. Paul and Seymour Newman (Academic, New York, 1978).
- ¹⁸ I.C. Sanchez and R. H. Lacombe, Macromolecules **11**, 1145 (1978).
- ¹⁹ C.R. Milchev, Acad. Bulg. Sci. **36**, 1415 (1983).
- ²⁰ E.A. Di Marzio, J.H. Gibbs, P. D. Fleming III, and I. C. Sanchez, Macromolecules **9**, 763 (1976).
- ²¹ D. Huang, S.L. Simon, and G.B. McKenna, J. Chem. Phys. **119**, 3590 (2003); *ibid.* **122**, 084907 (2005).
- ²² G.P. Johari, E. Tombari, S. Presto, and G. Salvetti, J. Chem. Phys. **117**, 5086 (2002).
- ²³ J. Wang and G.P. Johari, J. Chem. Phys. **116**, 2310 (2002).
- ²⁴ E.A. DiMarzio and F. Dowell, J. Appl. Phys. **50**, 6061 (1979).